

3D-melting features of the irreversibility line in overdoped $\text{Bi}_2\text{Sr}_2\text{CuO}_6$ at ultra-low temperature and high magnetic field

A. Morello^{ab*}, A.G.M. Jansen^a, R.S. Gonnelli^b and S.I. Vedenev^c

^aHigh Magnetic Field Laboratory, Max Planck Institut für Festkörperforschung and Centre National de la Recherche Scientifique, BP166, 38042 Grenoble Cedex 9, France

^bINFM - Dipartimento di Fisica, Politecnico di Torino, c.so Duca degli Abruzzi 24, 10129 Torino, Italy

^cP.N. Lebedev Physical Institute, Russian Academy of Sciences, SU-117924 Moscow, Russia

We have measured the irreversible magnetization of an overdoped $\text{Bi}_2\text{Sr}_2\text{CuO}_6$ single crystal up to $B = 28$ T and down to $T = 60$ mK, and extracted the irreversibility line $B_{\text{irr}}(T)$: the data can be interpreted in the whole temperature range as a 3D-anisotropic vortex lattice melting line with Lindemann number $c_L = 0.13$. We also briefly discuss the applicability of alternative models such as 2D- and quantum melting, and the connection with magnetoresistance experiments.

1. INTRODUCTION

Despite the deep structural and physical similarities with the wide family of Bi- and Tl-based high- T_c compounds, the layered cuprate superconductor $\text{Bi}_2\text{Sr}_2\text{CuO}_6$ (Bi-2201) has a relatively low critical temperature (typically less than 13 K). On the other hand, this is accompanied by a value of the upper critical field B_{c2} which lies within the experimentally accessible range, thus allowing the investigation of the whole $B - T$ phase diagram. Nevertheless, difficulties in growing high-quality single crystals have made this material much less studied than the other cuprates. In this work we present the results of irreversible magnetization measurements, carried out up to the applied magnetic field $B_a = 28$ T and down to $T = 60$ mK on a Bi-2201 single crystal. The goal of this work is to extract the irreversibility line $B_{\text{irr}}(T)$ and deduce what is the most suitable model to interpret its behavior, especially in view of the high anisotropy of the material and the influence of flux motion in the resistive transitions in magnetic field.

2. EXPERIMENT

The investigated sample is a high-quality $\text{Bi}_{2+x}\text{Sr}_{2-(x+y)}\text{Cu}_{1+y}\text{O}_{6\pm\delta}$ single crystal of approximate size $1100 \times 700 \times 10 \mu\text{m}^3$, intrinsically overdoped because of the Bi excess localized on the Sr positions; accordingly, we found a critical temperature $T_c \approx 4$ K. The magnetization was detected by means of a very sensitive capacitive torquemeter, installed into the mixing chamber of a dilution refrigerator. The plane of the torquemeter was tilted in order to have an angle $\theta = 30^\circ$ between the c -axis of the sample and the direction of the applied magnetic field. The torque loops $\tau(B)$ (inset of Fig. 1) were recorded during two independent sets of experiments, sweeping the field at the rates $dB_a/dt = 10.8$ mT/s and $dB_a/dt = 15$ mT/s, respectively. The magnetization loops $M(B)$ can be obtained from the relationship $M = \tau/(B_a \sin \theta)$. Calling $B_{\text{irr}}^{(a)}$ the applied field corresponding to the vanishing of the irreversible torque, the actual irreversibility field B_{irr} that would be obtained for $\mathbf{B}_a \parallel \mathbf{c}$ is given by $B_{\text{irr}} = B_{\text{irr}}^{(a)} \cos \theta$; this is due to the high anisotropy of Bi-2201, implying that only the field orthogonal to the ab -planes is effective.

*Present address: Kamerlingh Onnes Laboratory - Leiden University, P.O. Box 9504, NL 2300 RA Leiden, The Netherlands.

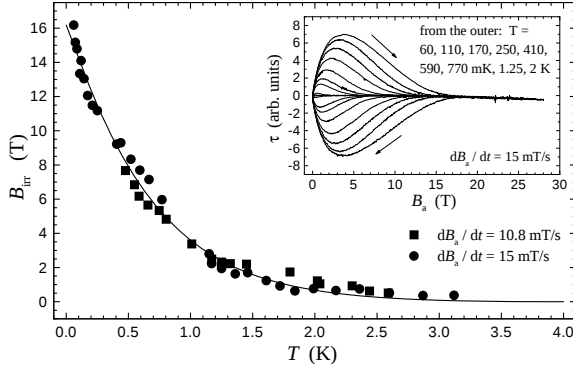


Figure 1. The irreversibility line of our Bi-2201 sample can be fitted to the 3D-anisotropic vortex lattice melting line as calculated from the Lindemann criterion, yielding $c_L = 0.13$ (solid line). The inset shows that all the torque loops have a typical shape that only scales with temperature.

3. DISCUSSION

The irreversibility line $B_{\text{irr}}(T)$ obtained in this way is shown in Fig. 1: qualitatively, it is very similar to the resistive upper critical field recently obtained with crystals very similar to ours [1], provided that the criterion $\rho/\rho_n = 0.1$ (i.e. the "foot" of the resistive transition) is chosen. This confirms that, in very anisotropic superconductors, there is a wide area of the $B - T$ phase diagram where the resistive transition is influenced by flux motion. On the other hand, this $B_{\text{irr}}(T)$ can not be interpreted in a simple depinning or flux creep picture, since its curvature does not correspond to a law $(1 - T/T_c)^n$ with $n \leq 2$. Here we show that the flux motion above B_{irr} takes place as a consequence of the melting of a 3D-anisotropic flux lattice, as demonstrated by the very good fit (solid line in Fig. 1) provided by the analytical form of the 3D-melting line $B_m(T)$ as calculated from the Lindemann criterion [2]:

$$B_m(T) = B_{c2}(0) \frac{4\vartheta^2}{\left(1 + \sqrt{1 + 4\vartheta T_s/T}\right)^2} \quad (1)$$

where $\vartheta = c_L^2 \sqrt{\beta_m/Gi} (T_c/T - 1)$, $T_s = T_c c_L^2 \sqrt{\beta_m/Gi}$, c_L is the Lindemann number, $Gi = \frac{1}{2} \left(\frac{\gamma k_B T_c}{(4\pi/\mu_0) B_c^2(0) \xi_{ab}^3(0)} \right)^2$ is the Ginzburg number, $\gamma = \sqrt{m_c/m_{ab}}$ is the mass anisotropy, $\kappa = \lambda_{ab}(0)/\xi_{ab}(0)$ and $\beta_m \approx 5.6$. With parameters appropriate for Bi-2201, the fit to Eq. (1) yields the very reasonable estimate of $c_L = 0.13$, very close to the value $c_L = 0.14$ predicted for 3D vortex lattice melting in high magnetic field [3]. It is interesting to observe that Eq. (1) is obtained using a linear extrapolation of B_{c2} down to $T = 0$, and here it provides a good fit down to $T/T_c \sim 0.01$: a fully linear behavior of $B_{c2}(T)$ is indeed found in Bi-2201 [1] taking the saturation points of the magnetoresistive transitions.

The high anisotropy of Bi-2201 might suggest that a more realistic picture for the vortex system is a stack of weakly coupled 2D pancake vortices [4]. Instead, our data do not agree neither qualitatively nor quantitatively to the predicted existence of a 2D-3D crossover field B_{cr} and a field-independent melting temperature T_m^{2D} in the $B - T$ phase diagram; also the almost identical shape of the torque loops at different temperatures (inset of Fig. 1) suggests the existence of only one pinning mechanism. We can also rule out a possible quantum melting of the vortex lattice at low temperatures [5], since we don't find any low- T linear features in $B_{\text{irr}}(T)$.

In conclusion, we can interpret the irreversibility line of overdoped $\text{Bi}_{2+x}\text{Sr}_{2-(x+y)}\text{Cu}_{1+y}\text{O}_{6\pm\delta}$ as the signature of 3D-anisotropic vortex lattice melting down to $T/T_c \sim 0.01$.

REFERENCES

1. S.I. Vedenev, A.G.M. Jansen, E. Haanappel and P. Wyder, Phys. Rev. B 60 (1999) 12467.
2. G. Blatter, M.V. Feigel'man, V.B. Geshkenbein, A.I. Larkin, V.M. Vinokur, Rev. Mod. Phys. 68 (1994) 1125, Eq. (5.10).
3. S. Hikami, A. Fujita, and A.I. Larkin, Phys. Rev. B 44 (1991) 10400.
4. L.I. Glazman, A.E. Koshelev, Phys. Rev. B 43 (1991) 2835, and references therein.
5. G. Blatter and B. Ivlev, Phys. Rev. Lett. 70 (1993) 2621.